

Purcell Enhancement of a Single Silicon Carbide Color Center with Coherent Spin Control

Alexander L. Crook, Christopher P. Anderson, Kevin C. Miao, Alexandre Bourassa, Hope Lee, Sam L. Bayliss, David O. Bracher, Xingyu Zhang, Hiroshi Abe, Takeshi Ohshima, Evelyn L. Hu, and David D. Awschalom*

Cite This: *Nano Lett.* 2020, 20, 3427–3434

Read Online

ACCESS |


Metrics & More

Article Recommendations

Supporting Information

ABSTRACT: Silicon carbide has recently been developed as a platform for optically addressable spin defects. In particular, the neutral divacancy in the 4H polytype displays an optically addressable spin-1 ground state and near-infrared optical emission. Here, we present the Purcell enhancement of a single neutral divacancy coupled to a photonic crystal cavity. We utilize a combination of nanolithographic techniques and a dopant-selective photoelectrochemical etch to produce suspended cavities with quality factors exceeding 5000. Subsequent coupling to a single divacancy leads to a Purcell factor of ~ 50 , which manifests as increased photoluminescence into the zero-phonon line and a shortened excited-state lifetime. Additionally, we measure coherent control of the divacancy ground-state spin inside the cavity nanostructure and demonstrate extended coherence through dynamical decoupling. This spin-cavity system represents an advance toward scalable long-distance entanglement protocols using silicon carbide that require the interference of indistinguishable photons from spatially separated single qubits.

KEYWORDS: Silicon carbide, divacancy, single spin defect, Purcell enhancement, coherent spin control, photonic crystal cavity

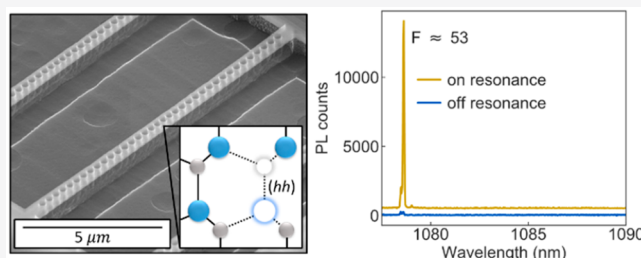

Silicon carbide (SiC) is a technologically mature semiconductor used in commercial applications ranging from high-power electronics to light-emitting diodes. These commercial uses have led to well-developed wafer-scale fabrication processes and precise control of doping during single-crystal growth. Concurrently, SiC has generated interest for low-loss nanophotonics, nonlinear optical phenomena, and microelectromechanical systems (MEMS).^{1–3} Recently, SiC has also shown promise as a host for optically addressable spin defects. These include the neutral divacancy (VV^0), the silicon vacancy (V_{Si}), and substitutional transition-metal ions (Cr^{4+} , V^{4+} , Mo^{5+}), among others.^{4–16} For these defects, isolated electronic states formed in the band gap create spin sublevels. The spin state can then be manipulated with applied microwave fields and read out using their distinct levels of photoluminescence (PL) after optical excitation. Experiments have utilized this optical readout mechanism to demonstrate control of the ground-state spin, forming the basis of a qubit.^{5,9,12,13} Additionally, the near-infrared emission of many of these SiC defects makes them compatible with existing fiber optic networks that operate at telecom wavelengths. For the V_{Si} and VV^0 , investigation of the excited-state optical fine structure has also revealed spin-preserving transitions that can be individually addressed in high-quality samples.^{17,18} The combination of ground-state spin control with optical spin readout using these transitions lays the foundation for a high-


fidelity spin-to-photon interface, with potential applications in quantum communication, distributed quantum computing, and quantum sensing.

For point-defect qubits in semiconductors such as SiC, an overarching goal is the development of a long-distance interconnected quantum network, where electron spins act as stationary qubit nodes interconnected by single photons acting as carriers of quantum information.¹⁹ This architecture could then be utilized as a “quantum repeater” to relay quantum states over length scales beyond the ~ 100 km limit of single photons through fiber.^{20,21} However, entanglement rates and scalability are limited by intrinsic emission into the zero-phonon line (ZPL), which is used to produce indistinguishable photons for interference between spatially separated spins. To this end, the defect spin community has explored using photonic nanocavities to enhance a coupled defect’s ZPL emission. This enhancement is typically expressed as the

Received: January 24, 2020

Revised: March 23, 2020

Published: March 25, 2020



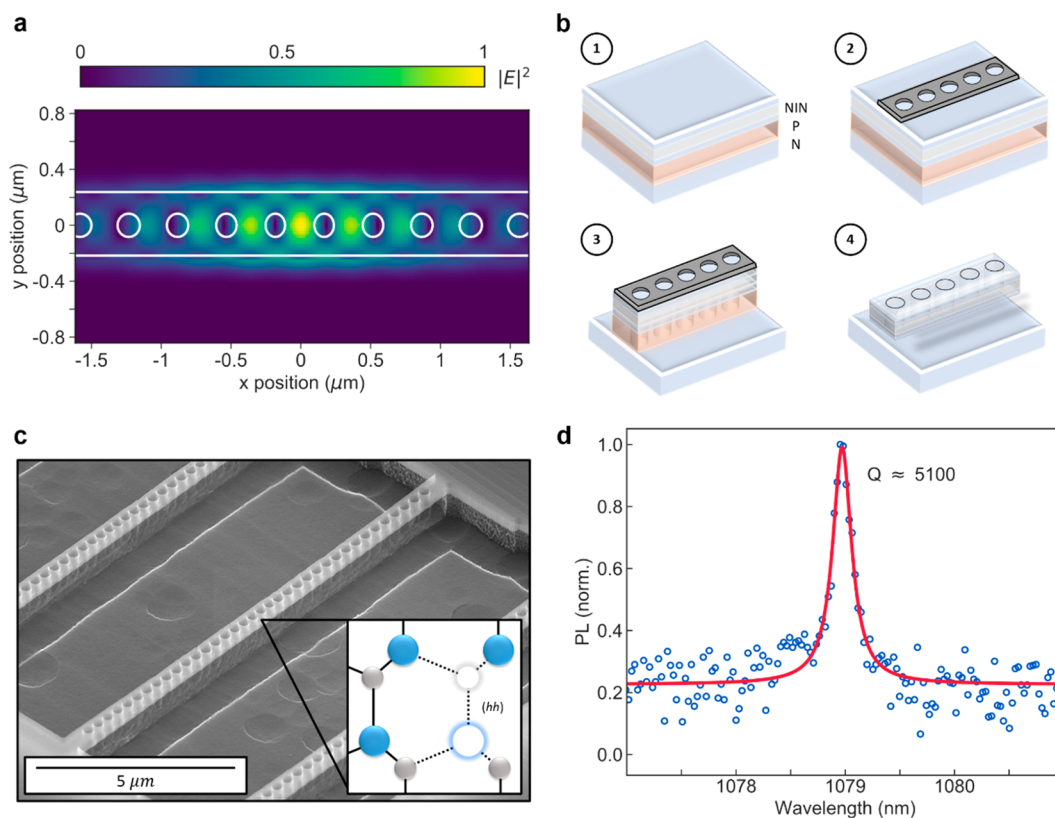


Figure 1. Nanobeam photonic cavities in 4H silicon carbide. (a) Simulation of nanobeam cavity mode performed with *Lumerical FDTD*, with a simulated quality factor of $Q \approx 3 \times 10^5$. (b) Outline of fabrication procedure. (1) A NINPN doped SiC chip is used as the starting material, where N denotes n-type, I denotes intrinsically doped with residual dopants, and P denotes p-type. (2) Electron beam lithography defines a 25 nm thick nickel mask. (3) A SF_6 -based ICP etch transfers the mask pattern to the SiC substrate. (4) A PEC selectively etches p-type SiC and creates an undercut structure. (c) SEM image of fabricated photonic crystal nanobeam cavities. (inset) A lattice representation of the (hh) VV^0 . (d) Photoluminescence spectrum of a nanobeam cavity taken at room temperature, showing a quality factor of ~ 5100 extracted from the full-width at half-maximum (fwhm) of a Lorentzian fit.

Purcell factor, which quantifies an excited state's lifetime reduction as a ratio of emission rates²²

$$F \equiv \frac{\Gamma_{\text{cavity}}}{\Gamma_{\text{bulk}}} = F_1 \cdot F_2 \cdot \frac{3Q}{4\pi^2 V} \left(\frac{\lambda_{\text{cavity}}}{n} \right)^3 + 1 \quad (1)$$

where Γ_{cavity} and Γ_{bulk} are the cavity-enhanced and unmodified emission rates, with $F = 1$ defining no enhancement. For the photonic cavity, Q is the quality factor, V is the mode volume, λ_{cavity} is the resonant wavelength, and n is the index of refraction. The terms F_1 and F_2 represent spatial overlap and spectral matching between the emitter and cavity mode, respectively, and are both equal to 1 in the case of perfect coupling (see [Supporting Information](#)). In recent work, cavity-defect systems in both diamond and silicon carbide have featured photonic crystal cavities with high quality factors ($\sim 10^3$ – 10^4) and small mode volumes ($\sim (\lambda/n)^3$).^{23–30} For silicon carbide, in particular, its high- Q nanophotonic capabilities,^{31,32} intrinsic spin-defect emitters, and wafer-scale doping control situates it to be a highly promising platform for integrated spin-photonic systems. However, despite SiC's potential, photonic integration with single VV^0 s remained unexplored.

In this Communication, we fabricate nanobeam photonic crystal cavities in 4H-SiC and couple them to single VV^0 s. We start with a description of the photonic cavity design and fabrication process. We then characterize a single VV^0 within

the cavity structure at cryogenic temperatures. When the cavity is tuned into resonance with the VV^0 , we observe a Purcell enhancement of ~ 50 and an improvement of the Debye–Waller (DW) factor from $\sim 5\%$ to ~ 70 – 75% . Lastly, we demonstrate microwave control of the ground-state spin and measure spin coherence times. This union between single defect control and cavity-emitter interactions results in significant increases in the VV^0 's ZPL emission with coherent electron spin states, establishing important groundwork for single-shot readout and scalable remote spin entanglement using defect spins.

Cavity Fabrication and Characterization. To create a photonic nanocavity, light must be confined in all three dimensions. Archetypal structures employ a submicron thin slab of dielectric material to provide out-of-plane confinement through total internal reflection and a patterning of Bragg mirrors to provide in-plane confinement. This results in either a one-dimensional (1D) or two-dimensional (2D) photonic crystal design, with both systems demonstrating high quality factors with small mode volumes.^{33,34} For this work, we select a 1D nanobeam structure due to its more compact size and successful demonstration in previous work.^{26,27} We use the general design outlined in work by Bracher et al.,²⁷ where circular holes are tapered to ellipses at the center of the nanobeam. This forms a photonic cavity, with a simulation of the resonant mode shown in [Figure 1a](#) and simulated quality factors typically in the range of $\sim 10^5$ – 10^6 .

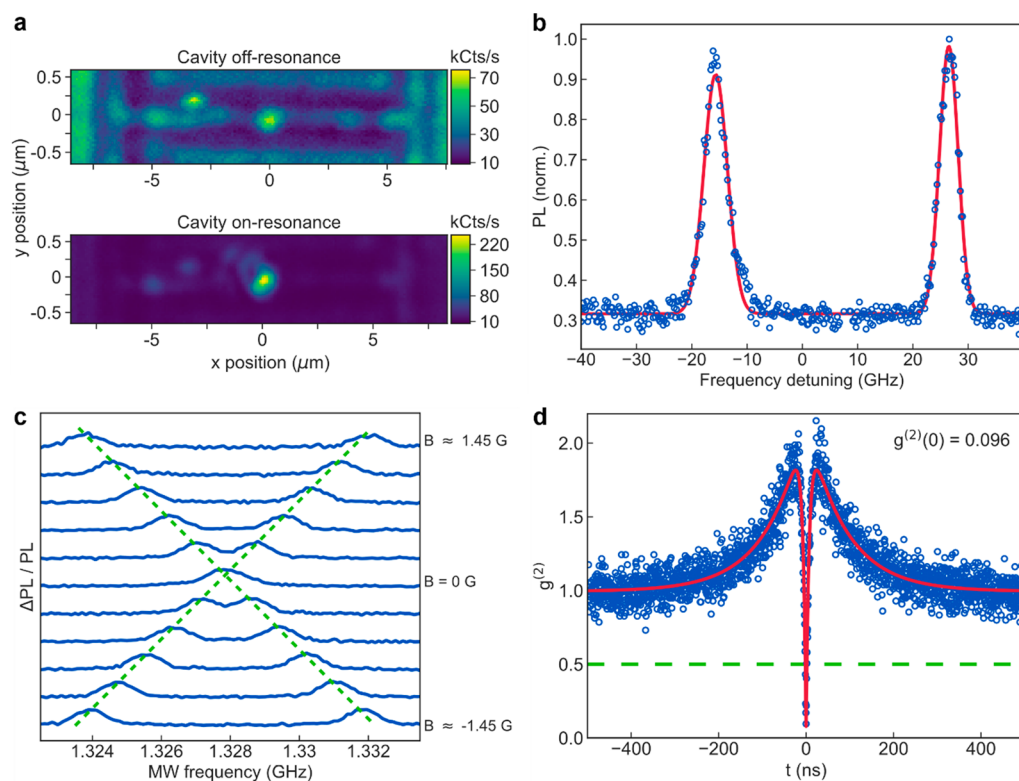


Figure 2. Single VV^0 spin qubit in a photonic crystal cavity. (a) Spatial PL scan around a photonic nanobeam cavity under off-resonant excitation with the cavity on (top) and off (bottom) resonance with an embedded VV^0 . (b) PLE scan over the central VV^0 in the nanobeam. Detuning is with respect to 278.000 THz. Peaks are present at 277.984 and 278.027 THz with fwhm Gaussian line widths of 5.02 ± 0.08 and 3.98 ± 0.06 GHz, respectively, with 95% confidence intervals. (c) ODMR of the nanobeam VV^0 under resonant excitation and varying applied magnetic fields. Separate scans are offset for clarity, and the green dotted lines are guides showing a linear Zeeman splitting. Magnetic field strengths vary between ± 1447 mG in uniform steps of ~ 289 mG. (d) $g^{(2)}(t)$ autocorrelation measurement of the nanobeam VV^0 , with a best fit (red) including the presence of a nonradiative state and a horizontal line (green) at $g^{(2)} = 0.5$ indicating the upper threshold for a single emitter. The data contain $g^{(2)}(0) = 0.096$ with no background subtraction, and the best fit line gives $g^{(2)}(0) = 0.079$. All measurements were taken at 5 K.

To form the nanobeam cavities, we utilize electron beam lithography for in-plane patterning and photoelectrochemical (PEC) etching for creating an undercut structure.^{35,36} The fabrication procedure, outlined in Figure 1b, begins with electron beam lithography to define a thin nickel mask with evaporation and liftoff. Next, a SF_6 -based inductively coupled plasma (ICP) etches through the silicon carbide in the regions not protected by the nickel. After an acid clean to remove the metal, a PEC etch and subsequent HF clean selectively etches the layer of p-type 4H-SiC 400 nm below the top surface, suspending the nanobeams. A scanning electron microscopy (SEM) image of a representative device is shown in Figure 1c. The nanobeams appear smooth both on the topside and sidewalls of the beams, with relatively smooth and vertical etched holes. We employed a variety of cavity dimensions to create cavity resonances that include ZPLs for each of the (hh), (kk), and (kh) VV^0 s (see Supporting Information for nomenclature). Several resulting cavities were then characterized for optical resonances with photoluminescence spectra collected using 905 nm excitation. For one such nanobeam, we measured a quality factor of ~ 5100 (Figure 1d) that was typical for photonic cavities in this sample.

Single VV^0 Characterization. After creating defects with an electron irradiation procedure (see Supporting Information), we characterize a single VV^0 coupled to the cavity in Figure 1d. Figure 2a shows a spatial PL scan taken at 5 K with off-resonant (905 nm) excitation and the cavity off/on

resonance with an ~ 1078 nm VV^0 transition. Subsequent photoluminescence excitation (PLE) measurements reveal two peaks at frequencies of 277.984 and 278.027 THz (Figure 2b). We then perform pulsed optically detected magnetic resonance (ODMR) with resonant optical excitation and a nearby wire-bond to drive microwave spin transitions. This results in an ODMR peak centered at 1.328 GHz (Figure 2c, center), which is closest to the (hh) VV^0 transition at 1.336 GHz.³⁷ As we vary the strength of an applied c -axis oriented magnetic field, this resonance separates into two lines due to a Zeeman splitting (Figure 2c). The observed shifts at ~ 2.76 MHz/G match closely with the electron gyromagnetic ratio of 2.8 MHz/G found in the c -axis (hh) and (kk) defects.³⁷ The presence of only one ODMR peak under zero magnetic field indicates that the transverse zero-field splitting (E) is approximately zero in the VV^0 spin Hamiltonian,⁵ which is also consistent with a c -axis oriented VV^0 . If we instead apply off-resonant optical excitation, we observe ODMR with a negative contrast that matches previous work with (hh) VV^0 s³⁷ (see Supporting Information). Thus, while the ZPL of this defect matches the (kh) VV^0 wavelength (~ 1078 nm), the c -axis spin orientation and the off-resonant ODMR contrast sign indicate the presence of an (hh) VV^0 . We attribute this behavior to a highly strained environment (see Supporting Information), likely due to the high doping levels used during growth.^{38–41}

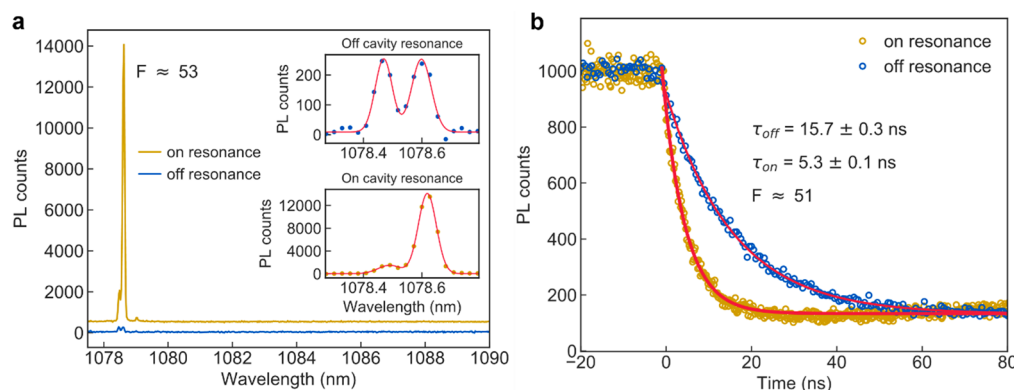


Figure 3. Purcell enhancement of a single VV^0 in a photonic crystal cavity. (a) Emission spectrum of the VV^0 when excited with off-resonant 905 nm laser light with the cavity on (inset, lower right) and off (inset, upper right) resonance with the lower energy branch. A ratio of emission intensities gives a Purcell factor of ~ 53 . The on-resonance trace for the combined plot is vertically offset for clarity. (b) Lifetime measurements of the VV^0 under resonant 277.984 THz excitation with the cavity on and off resonance. Fits to an exponential decay of $\exp(-t/\tau)$ give a shortened lifetime ($\tau = 5.3 \pm 0.1$ ns) when on resonance vs off resonance ($\tau = 15.7 \pm 0.3$ ns) with 95% confidence intervals, giving a Purcell factor of ~ 51 . All measurements were taken at 5 K.

Additionally, we confirm the presence of a single optical emitter with a second-order correlation measurement under resonant excitation (Figure 2d). The antibunching dip $g^{(2)}(0) \leq 0.5$ indicates the presence of a single emitter, and the value $g^{(2)}(0) = 0.096$ indicates that this VV^0 is an excellent single-photon source. Meanwhile, the observed bunching behavior is indicative of nonradiative transitions from the excited state. Solving the rate equations for this system (see Supporting Information) and fitting it to the observed $g^{(2)}$ gives an effective dark state lifetime of $\tau_{\text{dark}} \approx 60.7$ ns. The nonradiative transitions are likely a combination of intersystem crossing (ISC) decays and VV^0 ionization. Although the ISC rates have not been explored in 4H-SiC VV^0 s, in the 3C VV^0 they were estimated to be on a similar time scale of ~ 50 – 100 ns¹⁷. Additionally, VV^0 ionization can be observed in our experiment under lower laser powers as a blinking behavior. Without a sufficiently strong 905 nm charge reset pulse, the VV^0 may be trapped in a nonradiative charge state for long periods of time, as has been observed in other work.^{42,43}

Purcell Enhancement. With a tunable photonic nanocavity and a VV^0 emitter within its mode volume, we are able to observe Purcell enhancement of the VV^0 's optical emission. When the cavity is off resonance with the VV^0 and addressed with an off-resonant 905 nm laser, two peaks at ~ 1078 nm can be observed in a PL spectrum (Figure 3a, top inset). These peak locations and their ~ 40 GHz splitting correspond to the PLE peaks observed under resonant excitation (Figure 2b). We will label the lower/higher energy transitions as the lower/upper branches of the orbital fine structure, respectively.¹⁷ When the cavity is then tuned into resonance with the defect, a significant increase in emission is observed, with selective enhancement of the lower branch shown in Figure 3a. This count rate increase correlates closely with the Purcell factor, which in this case is given by

$$F = \frac{I_{\text{ZPL, on}}}{I_{\text{ZPL, off}}} \quad (2)$$

where $I_{\text{ZPL, on}}$ and $I_{\text{ZPL, off}}$ represent the ZPL intensity when the cavity is on resonance and blueshifted off resonance, respectively. This equation matches the form of eq 1, with ZPL intensities acting as measures of emission rates. Integrating the counts under the two peaks when off and on

cavity resonance gives Purcell factors of ~ 53 (Figure 3a) and ~ 16 (see Supporting Information) for the lower and upper branches, respectively. This difference could be explained by differing optical dipole orientations of the two branches, which would give varied matching to the cavity mode. A similar effect was observed for cavity enhancement of V_{Si} defects in silicon carbide, which also displays two rotated optical dipoles.²⁷

To corroborate the presence of Purcell enhancement, we directly measured excited-state lifetimes with the cavity on and off resonance with the VV^0 . Using resonant excitation pulses from an electro-optic modulator, we observe an off-resonance lifetime of $\tau_{\text{off}} = 15.7 \pm 0.3$ ns (consistent with bulk measurements¹⁷) and an on-resonance lifetime of $\tau_{\text{on}} = 5.3 \pm 0.1$ ns (Figure 3b). The relationship between measurable lifetimes and the Purcell factor is given by

$$F = \frac{\tau_{\text{dark}}(\tau_{\text{off}} - \tau_{\text{on}})}{\alpha\tau_{\text{on}}(\tau_{\text{dark}} - \tau_{\text{off}})} + 1 \quad (3)$$

where, for the VV^0 , τ_{dark} is the combined lifetime of all nonradiative decays, τ_{off} is the lifetime off cavity resonance, τ_{on} is the lifetime on cavity resonance, and α is the intrinsic DW factor (see Supporting Information). Combining our measurements with a previously measured $\sim 5.3\%$ DW factor¹⁷ gives a Purcell factor of $F \approx 51$, which is in good agreement with the value of $F \approx 53$ from spectral measurements.

One of the direct consequences of a Purcell enhancement is an increased Debye–Waller factor, which follows the relation

$$F = \frac{\beta(\alpha - 1)}{\alpha(\beta - 1)} \quad (4)$$

where α and β represent the VV^0 's DW factor off and on cavity resonance, respectively (see Supporting Information). For our sample, spatially varying background luminescence from nitrogen vacancy (NV) centers in the n-doped silicon carbide^{6,7,16,44} makes it difficult to directly integrate spectrometer counts to obtain α and β . However, we do observe background-subtracted count rates of 120 and 460 kCts/s when off and on cavity resonance, which allows us to estimate an on-resonance DW factor of $\beta \approx 75\%$ and a Purcell factor of $F \approx 54$ (see Supporting Information). These numbers match well with the Purcell factors of ~ 53 and ~ 51 obtained from Figure 3 and the corresponding 74% DW factor from eq

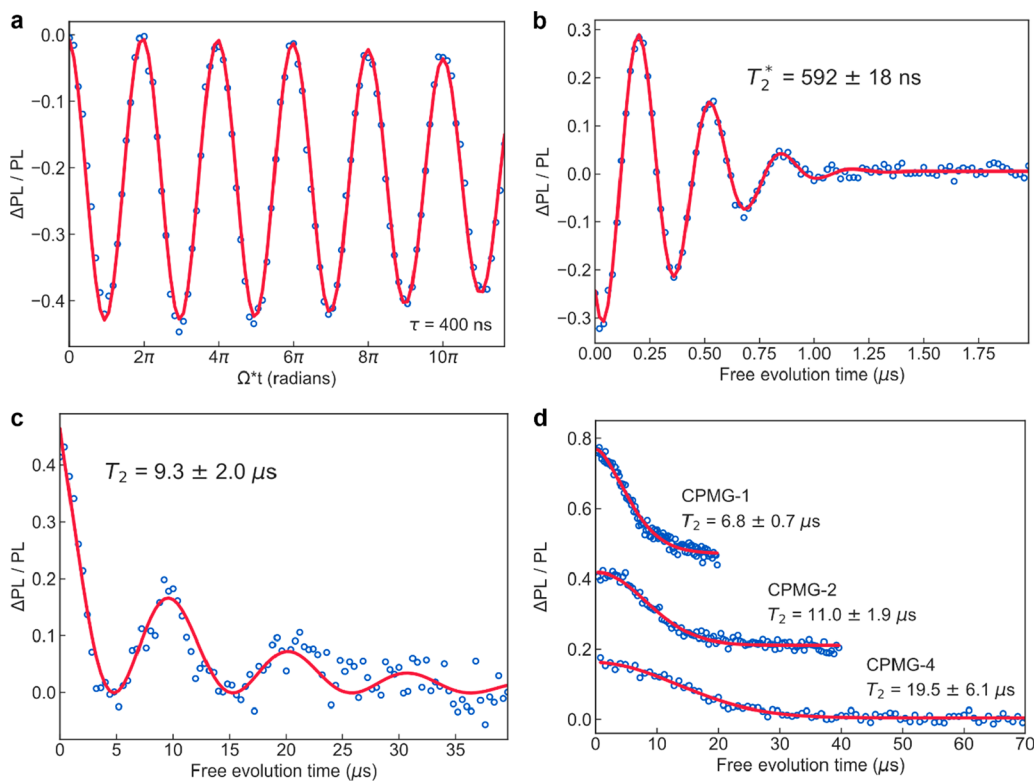


Figure 4. Coherent spin control of VV^0 in photonic crystal cavity. (a) Rabi oscillations between the $|l0\rangle$ and $|l+1\rangle$ states under an ~ 6 G c -axis magnetic field. The MW pulse length is kept constant at 400 ns, while the applied power is increased. (b) Ramsey sequence collected 3 MHz detuned from resonance at an ~ 218 G c -axis magnetic field. Points are fitted to a sinusoid decaying as $\exp(-(t/T_2^*)^n)$, giving $T_2^* = 592 \pm 18$ ns and $n = 2.08 \pm 0.19$ with 95% confidence intervals. (c) Hahn echo sequence collected under an ~ 218 G c -axis magnetic field. Points are fitted to a \sin^2 decaying as $\exp(-(t/T_2)^n)$, giving $T_2 = 9.3 \pm 2.0$ μ s and $n = 0.80 \pm 0.17$ with 95% confidence intervals. (d) Dynamical decoupling with CPMG sequences to extend the T_2 decay time. Taken under an ~ 6 G c -axis magnetic field. Fits to $A \exp(-(t/T_2)^n)$ give $T_2 = 6.8 \pm 0.7$, $T_2 = 11.0 \pm 1.9$, and $T_2 = 19.5 \pm 6.1$ μ s for CPMG-1 (a regular Hahn echo sequence), CPMG-2, and CPMG-4, respectively. The corresponding n values are $n = 1.6 \pm 0.2$, $n = 2.0 \pm 0.4$, and $n = 2.1 \pm 0.6$. Confidence intervals are one standard deviation for the CPMG data. All data were collected on the $m_s = |l0\rangle \rightarrow |l+1\rangle$ transition. All measurements were taken at 5 K.

4. Given the agreement between these independent measurements, we infer that the VV^0 emits 70–75% into the ZPL when the cavity is on resonance. This is a significant improvement over the intrinsic $\sim 5\%$ DW factor for the VV^0 , and the Purcell-enhanced 460 kCts/s is among the highest count rates achieved for SiC spin defects. Combined with the lifetime reduction, this enhancement greatly aids in achieving single-shot readout and high entanglement rates in SiC.

Coherent Spin Control. While addressing the cavity VV^0 with resonant microwave pulses and resonant optical excitation, we drive coherent Rabi oscillations between the spin sublevels. To address a single microwave transition, we apply a small magnetic field of ~ 6 G parallel to the c -axis to Zeeman split the spin resonances and then focus on the $|l0\rangle$ to $|l+1\rangle$ transition at 5 K. Under these conditions, we observe Rabi oscillations with a readout contrast of $\sim 40\%$ (Figure 4a). This contrast level is significantly higher than the typical 10–15% observed for off-resonant Rabi oscillations⁵ but below the ~ 94 – 98% levels observed with resonant excitation.^{17,42,45} This indicates that individual optical spin transitions are moderately selective but still display a spectral overlap from the ~ 4 – 5 GHz PLE optical line widths broadened from spectral diffusion. Given that individual spin transitions for c -axis VV^0 s are typically separated by a few gigahertz,¹⁷ it should be possible to achieve higher contrast with a slight narrowing of line widths.

We then apply Ramsey interferometry and Hahn echo pulse sequences on the same $|l0\rangle \rightarrow |l+1\rangle$ transition to determine the spin dephasing and spin coherence times. Under a c -axis magnetic field of ~ 218 G, we obtain a dephasing time of $T_2^* = 592 \pm 18$ ns (Figure 4b) and a decoherence time of $T_2 = 9.3 \pm 2.0$ μ s (Figure 4c). Under a lower magnetic field of ~ 6 G, we obtain similar times of $T_2^* = 605 \pm 33$ ns and $T_2 = 7.4 \pm 0.6$ μ s (see Supporting Information), indicating that coherence in this sample is not primarily limited by the SiC nuclear spin bath.⁴⁶ Collectively these times are shorter than previous reports of $T_2^* \approx 1$ – 2 μ s and $T_2 \approx 1.2$ ms in bulk SiC c -axis VV^0 s,⁵ with the discrepancy likely arising from magnetic dipole interactions with electron spins from n-type dopants and surface charge traps.^{47,48} It is worth noting that, for a VV^0 located in an unfabricated NIN epilayer, we measure an improved $T_2^* = 4.01 \pm 0.38$ μ s and $T_2 = 200 \pm 27.6$ μ s under ~ 218 G (see Supporting Information). Therefore, it appears the fabrication process introduces additional decoherence sources, potentially from increased surfaces or crystal damage. However, there is a variety of approaches to offset these effects. The PEC undercut could likely be performed at lower doping levels, and postfabrication surface treatments could potentially be used to limit the presence of surface charge traps.^{49,50}

In the regime where T_1 is significantly longer than T_2 , it is possible to extend spin coherence through dynamical decoupling sequences. For the cavity VV^0 , in two separate

measurements we observe spin relaxation times of $T_1 = 1.02 \pm 0.47$ ms and $T_1 = 2.43 \pm 1.58$ ms, placing a lower bound of $T_1 \gtrsim 500$ μ s (see [Supporting Information](#)) and indicating that T_2 is not T_1 limited. This is expected for the VV^0 at cryogenic temperatures, where T_1 has been measured to be 8–24 ms at 20 K.³⁷ As a proof of principle, we then employ a Carr–Purcell–Meiboom–Gill (CPMG) sequence⁵¹ at low field with one, two, and four π pulses ([Figure 4d](#)). Stretched exponential fits give T_2 values of 6.8 ± 0.7 , 11.0 ± 1.9 , and 19.5 ± 6.1 μ s, indicating the viability to extend spin coherence in SiC nanostructures with dynamical decoupling up to the T_1 limit.

DISCUSSION

Experimentally, increases in both the Debye–Waller factor and PL count rate have significant implications for enhancing the entanglement generation rate between VV^0 spins. In the Barrett–Kok protocol,^{52,53} for example, the entanglement success rate is proportional to the square of the DW factor for two consecutive ZPL detection events. Using the $\sim 75\%$ DW factor measured here then gives a significant projected entanglement rate increase of $(0.75/0.053)^2 \approx 200$ between two (hh) VV^0 s. Additionally, entanglement verification relies on single-shot readout to determine the electron spin state in a single measurement,⁵⁴ which is ultimately limited by photon detection throughput. For this system, the Purcell-enhanced threefold lifetime decrease would correspond to triple the emission events before a spin flip. The overall increase of off-cavity-resonance PL (~ 120 kCts/s) compared to bulk VV^0 s (typically 40–50 kCts/s) is also indicative of a slightly improved collection efficiency. This is a vital factor for single-shot readout measurements, since a majority of PL from bulk VV^0 s is lost due to reflection and refraction at the SiC/air interface. Thus, both single-shot readout of VV^0 spin states in a photonic structure and photonically enhanced entanglement could be achievable in future studies.

The cavity-enhanced VV^0 studied here contains 4–5 GHz optical line widths comparable to those seen in near surface NV centers in diamond,⁵⁵ but above the lifetime limit of ~ 11 MHz.¹⁷ We attribute the broadened optical line widths to spectral diffusion originating from a fluctuating charge environment around the defect. These charge fluctuations could be from nearby doped regions, other nearby defects and impurities, or surface charge traps. It is worth noting that the optical line widths are broader in 400 nm suspended I-type SiC (~ 10 – 20 GHz) compared to the suspended NIN shown here (~ 4 – 5 GHz). Thus, doping configurations and growth conditions can have significant effects on spectral diffusion, opening the possibility to achieve narrow line widths through properly doped structures. Additionally, optical line widths are ~ 1 GHz for defects in the intrinsic layer of NINPN material before fabrication (see [Supporting Information](#)), indicating that the fabrication process or final nanostructure is a significant source of broadening. To counteract this effect, surface treatments⁵⁶ or applied voltages could be used to maintain narrow line widths. Under applied electric fields, for example, VV^0 optical line widths as narrow as ~ 20 MHz have been observed.^{42,45}

In conclusion, we have fabricated a photonic crystal cavity in silicon carbide coupled to a single VV^0 . We observe Purcell enhancement of the ZPL optical transition with a Purcell factor of ~ 50 , a subsequent increase in Debye–Waller factor from $\sim 5\%$ to ~ 70 – 75% , and coherent spin control of the VV^0 ground state with coherence extension. The use of a doped

nanostructure allows for potential electric field and charge control, in situ Stark tuning, and improved collection efficiencies for optimized geometries, all of which would provide further improvements to the VV^0 optical properties. As a whole, this system advances the robustness of spin-to-photon transduction for the VV^0 in a technologically mature material. Looking beyond to many-qubit architectures, photonic nanocavities will be a necessary component to maintain scalability across long-distance entanglement networks.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acs.nanolett.0c00339>.

Details on VV^0 creation procedure, SiC doping, fabrication details, VV^0 nomenclature conventions, and cavity tuning procedure. Additional cavity VV^0 spin coherence measurements and measurements with off-resonant optical excitation. Characterization of bulk defects in the NINPN material. Observation of Purcell enhancement of upper branch of the cavity VV^0 . Discussion of modeled cavity mode with relevant dimensions. Details on photoelectrochemical etching. Details on rate equations used to model the system. Derivations of Purcell factor expressions. Discussion of the effect of strain on the cavity VV^0 ([PDF](#))

AUTHOR INFORMATION

Corresponding Author

David D. Awschalom – Pritzker School of Molecular Engineering and Department of Physics, University of Chicago, Chicago, Illinois 60637, United States; Center for Molecular Engineering and Materials Science Division, Argonne National Laboratory, Lemont, Illinois 60439, United States; orcid.org/0000-0002-8591-2687; Email: awsch@uchicago.edu

Authors

Alexander L. Crook – Pritzker School of Molecular Engineering and Department of Physics, University of Chicago, Chicago, Illinois 60637, United States

Christopher P. Anderson – Pritzker School of Molecular Engineering and Department of Physics, University of Chicago, Chicago, Illinois 60637, United States

Kevin C. Miao – Pritzker School of Molecular Engineering, University of Chicago, Chicago, Illinois 60637, United States

Alexandre Bourassa – Pritzker School of Molecular Engineering, University of Chicago, Chicago, Illinois 60637, United States

Hope Lee – Pritzker School of Molecular Engineering and Department of Physics, University of Chicago, Chicago, Illinois 60637, United States

Sam L. Bayliss – Pritzker School of Molecular Engineering, University of Chicago, Chicago, Illinois 60637, United States; orcid.org/0000-0002-1156-7243

David O. Bracher – John A. Paulson School of Engineering and Applied Sciences and Department of Physics, Harvard University, Cambridge, Massachusetts 02138, United States

Xingyu Zhang – John A. Paulson School of Engineering and Applied Sciences, Harvard University, Cambridge, Massachusetts 02138, United States

Hiroshi Abe – National Institutes for Quantum and Radiological Science and Technology, Takasaki, Gunma 370-1292, Japan

Takeshi Ohshima – National Institutes for Quantum and Radiological Science and Technology, Takasaki, Gunma 370-1292, Japan; orcid.org/0000-0002-7850-3164

Evelyn L. Hu – John A. Paulson School of Engineering and Applied Sciences and Department of Physics, Harvard University, Cambridge, Massachusetts 02138, United States

Complete contact information is available at:
<https://pubs.acs.org/10.1021/acs.nanolett.0c00339>

Author Contributions

A.C. developed, fabricated, and measured the photonic crystal devices. C.A. and H.L. aided with fabrication procedures. C.A., K.M., and A.B. aided with optical characterization, cryogenic spin measurements, and analysis of data, S.B. assisted with resonant lifetime measurements and development of the three-level $g^{(2)}$ model. D.B., X.Z., and E.H. were instrumental in the development of both the PEC etch of SiC and SiC photonic devices. H.A. and T.O. performed electron irradiation of SiC samples to create divacancies. D.A. oversaw and directed the project. A.C., C.A., K.M., A.B., H.L., and S.B. all contributed with the drafting of the manuscript.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

This work was supported by the NSF EFRI ACQUIRE EFMA-1641099 and the Univ. of Chicago MRSEC DMR-1420709. (A.C.) This work was funded by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences. This work also made use of the Pritzker Nanofabrication Facility part of the Pritzker School of Molecular Engineering at the Univ. of Chicago, which receives support from Soft and Hybrid Nanotechnology Experimental (SHyNE) Resource (NSF ECCS-1542205), a node of the National Science Foundation's National Nanotechnology Coordinated Infrastructure. Electron irradiation was funded by Grant Nos. JSPS KAKENHI 17H01056 and 18H03770. This work was completed in part with resources provided by the Univ. of Chicago's Research Computing Center.

REFERENCES

- (1) Castelletto, S.; Rosa, L.; Johnson, B. C. Silicon Carbide for Novel Quantum Technology Devices. In *Advanced Silicon Carbide Devices and Processing*; Intech Open, 2015; pp 222–248.
- (2) Guo, X.; Xun, Q.; Li, Z.; Du, S. Silicon carbide converters and MEMS devices for high-temperature power electronics: A critical review. *Micromachines* **2019**, *10*, 406.
- (3) Zorman, C. A.; Parro, R. J. Micro- and nanomechanical structures for silicon carbide MEMS and NEMS. *Phys. Status Solidi B* **2008**, *245*, 1404–1424.
- (4) Koehl, W. F.; Buckley, B. B.; Heremans, F. J.; Calusine, G.; Awschalom, D. D. Room temperature coherent control of defect spin qubits in silicon carbide. *Nature* **2011**, *479*, 84–87.
- (5) Christle, D. J.; et al. Isolated electron spins in silicon carbide with millisecond coherence times. *Nat. Mater.* **2015**, *14*, 160–163.
- (6) Csóré, A.; Von Bardeleben, H. J.; Cantin, J. L.; Gali, A. Characterization and formation of NV centers in 3C, 4H, and 6H SiC: An ab initio study. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2017**, *96*, 085204.

(7) Wang, J. F.; et al. Coherent control of nitrogen-vacancy center spins in silicon carbide at room temperature. *arXiv*, 1909.12481 (2019). <https://arxiv.org/abs/1909.12481> (accessed 2020-03-24).

(8) Lohrmann, A.; Johnson, B. C.; McCallum, J. C.; Castelletto, S. A review on single photon sources in silicon carbide. *Rep. Prog. Phys.* **2017**, *80*, 034502.

(9) Widmann, M.; et al. Coherent control of single spins in silicon carbide at room temperature. *Nat. Mater.* **2015**, *14*, 164–168.

(10) Nagy, R.; et al. Quantum Properties of Dichroic Silicon Vacancies in Silicon Carbide. *Phys. Rev. Appl.* **2018**, *9*, 25–27.

(11) Nagy, R.; et al. High-fidelity spin and optical control of single silicon-vacancy centres in silicon carbide. *Nat. Commun.* **2019**, *10*, 1954.

(12) Wolfowicz, G.; et al. Vanadium spin qubits as telecom quantum emitters in silicon carbide. *arXiv*, 1908.09817 (2019). <https://arxiv.org/abs/1908.09817> (accessed 2020-03-24).

(13) Diler, B.; et al. Coherent control and high-fidelity readout of chromium ions in commercial silicon carbide. *npj Quantum Inf* **2020**, *6*, 11.

(14) Koehl, W. F.; et al. Resonant optical spectroscopy and coherent control of Cr⁴⁺ spin ensembles in SiC and GaN. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2017**, *95*, 035207.

(15) Bosma, T.; et al. Identification and tunable optical coherent control of transition-metal spins in silicon carbide. *npj Quantum Inf* **2018**, *4*, 48.

(16) Von Bardeleben, H. J.; et al. NV centers in 3C,4H, and 6H silicon carbide: A variable platform for solid-state qubits and nanosensors. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2016**, *94*, 121202.

(17) Christle, D. J.; et al. Isolated spin qubits in SiC with a high-fidelity infrared spin-to-photon interface. *Phys. Rev. X* **2017**, *7*, 021046.

(18) Banks, H. B.; et al. Resonant Optical Spin Initialization and Readout of Single Silicon Vacancies in 4H - Si C. *Phys. Rev. Appl.* **2019**, *11*, 024013.

(19) Wehner, S.; Elkouss, D.; Hanson, R. Quantum internet: A vision for the road ahead. *Science* **2018**, *362*, No. eaam9288.

(20) Briegel, H. J.; Dür, W.; Cirac, J. I.; Zoller, P. Quantum repeaters: The role of imperfect local operations in quantum communication. *Phys. Rev. Lett.* **1998**, *81*, 5932–5935.

(21) Childress, L.; Taylor, J. M.; Sørensen, A. S.; Lukin, M. D. Fault-tolerant quantum communication based on solid-state photon emitters. *Phys. Rev. Lett.* **2006**, *96*, 96–99.

(22) Pelton, M. Modified spontaneous emission in nanophotonic structures. *Nat. Photonics* **2015**, *9*, 427–435.

(23) Li, L.; et al. Coherent spin control of a nanocavity-enhanced qubit in diamond. *Nat. Commun.* **2015**, *6*, 6173.

(24) Calusine, G.; Politi, A.; Awschalom, D. D. Silicon carbide photonic crystal cavities with integrated color centers. *Appl. Phys. Lett.* **2014**, *105*, 011123.

(25) Calusine, G.; Politi, A.; Awschalom, D. D. Cavity-Enhanced Measurements of Defect Spins in Silicon Carbide. *Phys. Rev. Appl.* **2016**, *6*, 014019.

(26) Bracher, D. O.; Hu, E. L. Fabrication of High-Q Nanobeam Photonic Crystals in Epitaxially Grown 4H-SiC. *Nano Lett.* **2015**, *15*, 6202–6207.

(27) Bracher, D. O.; Zhang, X.; Hu, E. L. Selective Purcell enhancement of two closely linked zero-phonon transitions of a silicon carbide color center. *Proc. Natl. Acad. Sci. U. S. A.* **2017**, *114*, 4060–4065.

(28) Lukin, D. M.; Dory, C.; Mishra, S. D.; Guidry, M. A.; Radulaski, M.; et al. 4H-Silicon-Carbide-on-Insulator for Integrated Quantum and Nonlinear Photonics. *Nat. Photonics* **2019**, DOI: [10.1038/s41566-019-0556-6](https://doi.org/10.1038/s41566-019-0556-6).

(29) Hausmann, B. J. M.; et al. Coupling of NV centers to photonic crystal nanobeams in diamond. *Nano Lett.* **2013**, *13*, 5791–5796.

(30) Lee, J. C.; et al. Deterministic coupling of delta-doped nitrogen vacancy centers to a nanobeam photonic crystal cavity. *Appl. Phys. Lett.* **2014**, *105*, 261101.

- (31) Song, B.-S.; et al. Ultrahigh-Q photonic crystal nanocavities based on 4H silicon carbide. *Optica* **2019**, *6*, 991–995.
- (32) Lee, J. Y.; Lu, X.; Lin, Q. High-Q silicon carbide photonic-crystal cavities. *Appl. Phys. Lett.* **2015**, *106*, 041106.
- (33) Deotare, P. B.; McCutcheon, M. W.; Frank, I. W.; Khan, M.; Lončar, M. High quality factor photonic crystal nanobeam cavities. *Appl. Phys. Lett.* **2009**, *94*, 121106.
- (34) Sekoguchi, H.; Takahashi, Y.; Asano, T.; Noda, S. Photonic crystal nanocavity with a Q-factor of ~ 9 million. *Opt. Express* **2014**, *22*, 916–924.
- (35) Zhao, F.; Islam, M. M.; Huang, C. F. Photoelectrochemical etching to fabricate single-crystal SiC MEMS for harsh environments. *Mater. Lett.* **2011**, *65*, 409–412.
- (36) Pavunny, S. P.; et al. On the doping concentration dependence and dopant selectivity of photogenerated carrier assisted etching of 4H–SiC epilayers. *Electrochim. Acta* **2019**, *323*, 134778.
- (37) Falk, A. L.; et al. Polytype control of spin qubits in silicon carbide. *Nat. Commun.* **2013**, *4*, 1819.
- (38) Huh, S. W.; et al. Doping-induced strain and relaxation of Al-doped 4H-SiC homoepitaxial layers. *J. Appl. Phys.* **2004**, *96*, 4637–4641.
- (39) Jacobson, H.; et al. Doping-induced strain in N-doped 4H-SiC crystals. *Appl. Phys. Lett.* **2003**, *82*, 3689–3691.
- (40) Chung, H. J.; Liu, J. Q.; Henry, A.; Skowronski, M. Stacking Fault Formation in Highly Doped 4H-SiC Epilayers during Annealing. *Mater. Sci. Forum* **2003**, *433–436*, 253–256.
- (41) Okojie, R. S.; Holzheu, T.; Huang, X. R.; Dudley, M. X-ray diffraction measurement of doping induced lattice mismatch in n-type 4H-SiC epilayers grown on p-type substrates. *Appl. Phys. Lett.* **2003**, *83*, 1971–1973.
- (42) Anderson, C. P.; et al. Electrical and optical control of single spins integrated in scalable semiconductor devices. *Science* **2019**, *366*, 1225–1230.
- (43) Wolfowicz, G.; et al. Optical charge state control of spin defects in 4H-SiC. *Nat. Commun.* **2017**, *8*, 1876.
- (44) Zargaleh, S. A.; et al. Nitrogen vacancy center in cubic silicon carbide: A promising qubit in the 1.5 μ m spectral range for photonic quantum networks. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2018**, *98*, 165203.
- (45) Miao, K. C.; et al. Electrically driven optical interferometry with spins in silicon carbide. *Sci. Adv.* **2019**, *5*, No. eaay0527.
- (46) Seo, H.; et al. Quantum decoherence dynamics of divacancy spins in silicon carbide. *Nat. Commun.* **2016**, *7*, 12935.
- (47) Rosskopf, T.; et al. Investigation of surface magnetic noise by shallow spins in diamond. *Phys. Rev. Lett.* **2014**, *112*, 147602.
- (48) Barry, J. F.; et al. Sensitivity Optimization for NV-Diamond Magnetometry. *arXiv*, 1903.08176 (2019). <https://arxiv.org/abs/1903.08176> (accessed 2020-03-24).
- (49) Kim, M.; et al. Decoherence of Near-Surface Nitrogen-Vacancy Centers Due to Electric Field Noise. *Phys. Rev. Lett.* **2015**, *115*, 087602.
- (50) Fávoro De Oliveira, F.; et al. Effect of low-damage inductively coupled plasma on shallow nitrogen-vacancy centers in diamond. *Appl. Phys. Lett.* **2015**, *107*, 073107.
- (51) Meiboom, S.; Gill, D. Modified spin-echo method for measuring nuclear relaxation times. *Rev. Sci. Instrum.* **1958**, *29*, 688–691.
- (52) Barrett, S. D.; Kok, P. Efficient high-fidelity quantum computation using matter qubits and linear optics. *Phys. Rev. A: At., Mol., Opt. Phys.* **2005**, *71*, 060310.
- (53) Bernien, H.; et al. Heralded entanglement between solid-state qubits separated by three metres. *Nature* **2013**, *497*, 86–90.
- (54) Robledo, L.; et al. High-fidelity projective read-out of a solid-state spin quantum register. *Nature* **2011**, *477*, 574–578.
- (55) Faraon, A.; Santori, C.; Huang, Z.; Acosta, V. M.; Beausoleil, R. G. Coupling of nitrogen-vacancy centers to photonic crystal cavities in monocrystalline diamond. *Phys. Rev. Lett.* **2012**, *109*, 033604.
- (56) Liu, J.; et al. Single Self-Assembled InAs/GaAs Quantum Dots in Photonic Nanostructures: The Role of Nanofabrication. *Phys. Rev. Appl.* **2018**, *9*, 064019.