

SCIENTIFIC REPORTS



OPEN

Top-down fabrication of high-uniformity nanodiamonds by self-assembled block copolymer masks

Jiabao Zheng¹, Benjamin Lienhard¹, Gregory Doerk², Mircea Cotlet², Eric Bersin¹, Harrison Sejoon Kim³, Young-Chul Byun³, Chang-Yong Nam², Jiyoung Kim³, Charles T. Black² & Dirk Englund¹

Nanodiamonds hosting colour centres are a promising material platform for various quantum technologies. The fabrication of non-aggregated and uniformly-sized nanodiamonds with systematic integration of single quantum emitters has so far been lacking. Here, we present a top-down fabrication method to produce 30.0 ± 5.4 nm uniformly-sized single-crystal nanodiamonds by block copolymer self-assembled nanomask patterning together with directional and isotropic reactive ion etching. We show detected emission from bright single nitrogen vacancy centres hosted in the fabricated nanodiamonds. The lithographically precise patterning of large areas of diamond by self-assembled masks and their release into uniformly sized nanodiamonds open up new possibilities for quantum information processing and sensing.

Over the past two decades, solid-state defects have emerged as one of the leading systems for a wide variety of quantum technologies. Solid-state hosts such as diamond or silicon carbide are well studied, and a wide spectrum of fluorescing crystal defects have been identified and characterized^{1–5}. In particular, the diamond nitrogen vacancy (NV) centre with its optically-addressable long-lived spin system is well suited for applications ranging from quantum networks^{6,7} to quantum sensors⁸. Research interest has been growing considerably in developing other atomic emitters, such as the group-IV vacancy centres, possessing similar characteristics but with improved spectral stability^{9–12}.

Nanodiamonds (ND) hosting such colour centres are promising for various biological¹³ and quantum^{14–16} technologies, thanks in part to their compatibility with biologically active tissue and with common surface modification techniques^{13,17}. Furthermore, they have been employed for laser trapping techniques^{18–20} and scanning tip microscopy^{21–23}. In comparison with bulk diamond, NDs offer nanometre-scale spatial positioning and compatibility with optical levitation. Typical commercialized techniques for ND fabrication include detonation, laser ablation, balling milling, high-pressure high-temperature (HPHT) growth, and chemical vapor deposition (CVD) growth²⁴. However, these methods lack control over size or aggregation of the resulting NDs¹⁴. A reliable fabrication method of non-aggregated, uniform-sized, monocrystalline NDs with incorporated single colour centres is still challenging.

Control over the ND size uniformity is an important figure of merit for applications that involve building nano-hybrids²⁵, self-assembly processes^{26,27}, or integration with quantum emitters created via ion implantation²⁸. Controlling the ND size requires precise tuning of the detonation, milling, or growth process and is usually followed by an extra ultracentrifugation step. Furthermore, the separation of individual NDs²⁹ is an important requirement to prepare ND samples for subsequent integration with photonic nanostructures³⁰ or biological tissue³¹. Traditional methods require stabilizing agents which can introduce contamination during the sample preparation³². Furthermore, control of doping concentration in NDs is necessary for applications such as nanodiamond electronics³³ and optical levitation of NDs³⁴. Methods based on ion implantation²⁸ or detonation synthesis³⁵ are part of ongoing research.

¹Department of Electrical Engineering and Computer Science, Massachusetts Institute of Technology, Cambridge, Massachusetts, 02139, United States. ²Center for Functional Nanomaterials, Brookhaven National Laboratory, Upton, NY, 11973, USA. ³Department of Materials Science and Engineering, The University of Texas at Dallas, 800 West Campbell Road, Richardson, Texas, 75080, USA. Correspondence and requests for materials should be addressed to J.Z. (email: jz2466@columbia.edu) or D.E. (email: englund@mit.edu)

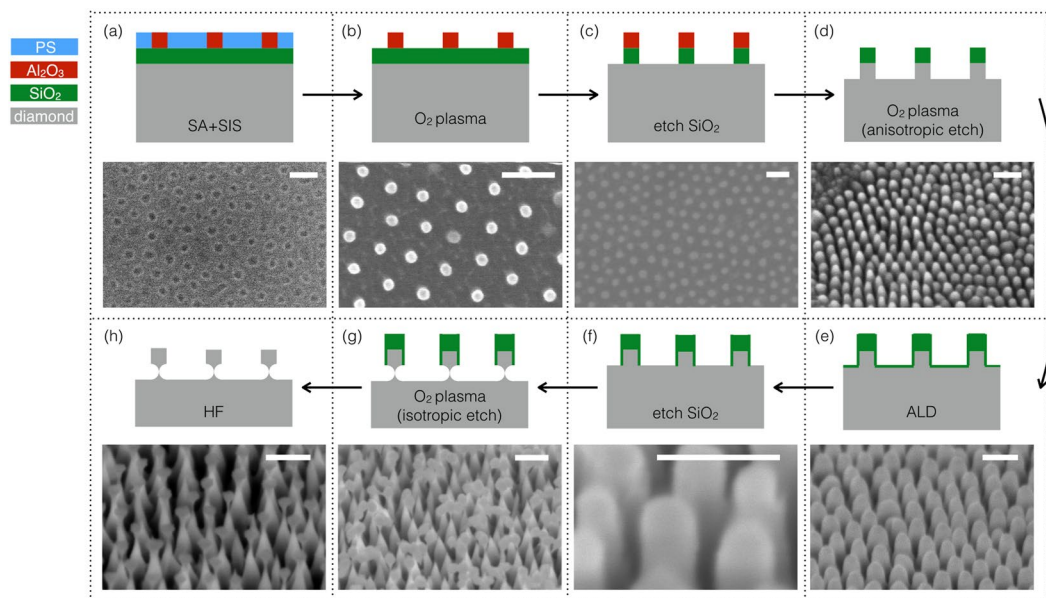


Figure 1. Fabrication process flow in 8 steps, with colour legend at upper left indicating the material of each layer. Each subfigure corresponds to one fabrication step, with schematic side-view diagram, and text showing the specific process carried out in the particular step, together with SEM images taken after that step, showing resultant device morphology. All scale bars indicate 100 nm. Note that images for steps (a–c) are top view, and images for other steps were obtained with samples tilted at 45 degrees. (a) Polished bulk single crystal diamond, coated with ~30 nm SiO₂ layer using PECVD, with AlO_x hexagonal dot array patterned by BCP film using spin coating, SA and SIS. (b) Gentle O₂ plasma treatment removes the polymer content in the BCP film, leaving AlO_x hexagonal dot array pattern. (c) Directional plasma etching of SiO₂, transferring the dot array pattern to SiO₂ layer. (d) Directional O₂ plasma etching of diamond, transferring the dot array pattern to bulk diamond, forming diamond pillars arranged in hexagonal array. (e) ALD of ~2 nm SiO₂ coating to protect the sidewall of etched diamond pillars. (f) A short directional plasma etch removes SiO₂ from bottom surfaces of the open gaps between diamond pillars. (g) The sample is exposed to a quasi-isotropic O₂ plasma to undercut the diamond pillars. (h) The bulk diamond is immersed in HF acid to remove the residue SiO₂ layer.

Solutions to these fabrication challenges have been explored, and while progress has been made, many problems still remain. A fabrication approach for reactive ion etching of NDs using a sputtered gold mask with mean particle diameters of 50 nm has been demonstrated and resulted in NDs hosting implanted NVs with spin coherence times, T_2 , exceeding 200 μ s³⁶. However, such sputtered gold masks suffer from significant non-uniformity, and the mechanical process utilized to release diamond nanopillars from the parent diamond causes loss of material. Another option to fabricate NDs is to use a CVD grown diamond membrane with a delta-doped NV layer³⁷. Electron beam lithography (EBL) and plasma etching can then be used to control the ND size. This technique enabled the demonstration of NVs in NDs with 200 nm diameter on average and a T_2 exceeding 700 μ s. However, the EBL fabrication of the mask is not scalable, and the resultant particles exceed the size requirements for many applications.

Here, we demonstrate large-scale parallel fabrication of non-aggregated, uniform-sized, monocrystalline NDs hosting single NV centres. The fabrication technique starts with CVD grown high-purity single-crystal diamond. It leverages the scalability of block copolymer (BCP) self-assembly combined with sequential infiltration synthesis to define nanometre-sized etching masks across an arbitrarily large diamond sample. A directional plasma etching step defines the dimensions of the NDs. An isotropic plasma etching step releases the NDs. We confirmed single-photon emission from single NVs hosted in the fabricated NDs. Statistics of the diameter of the released NDs indicate a mean diameter of about 30 nm with a variance of 5.4 nm.

Results

Our ND fabrication process starts with commercially available bulk monocrystalline diamond (Element Six) grown by a microwave-assisted CVD process. We use IIA optical grade monocrystalline diamond (size $3 \times 3 \times 0.5$ mm³) with a nitrogen concentration of less than 5 ppm (corresponding to ~12 nitrogen atoms for 30 nm diameter diamond spheres). We deposit a ~30 nm SiO₂ layer by plasma-enhanced chemical vapor deposition (PECVD) as an etch stop layer. As outlined in Fig. 1, the fabrication process proceeds as follows: (a) The mask array in a hexagonal lattice configuration is produced by BCP self-assembly (SA), followed by sequential infiltration synthesis (SIS)^{38,39} to selectively load dots with AlO_x to produce a hard etch mask that can withstand the subsequent reactive ion processing steps, see Supplemental Information (SI) for details. (b) Oxygen plasma reactive ion etching (RIE) removes the polymer, leaving only the AlO_x dots array pattern. (c) Dry etching of SiO₂ using SF₆ and oxygen plasma transfers the hexagonal dot array pattern into the SiO₂ etch stop layer. (d) Directional oxygen plasma etching transfers this SiO₂ dot array pattern into the diamond, producing a hexagonal

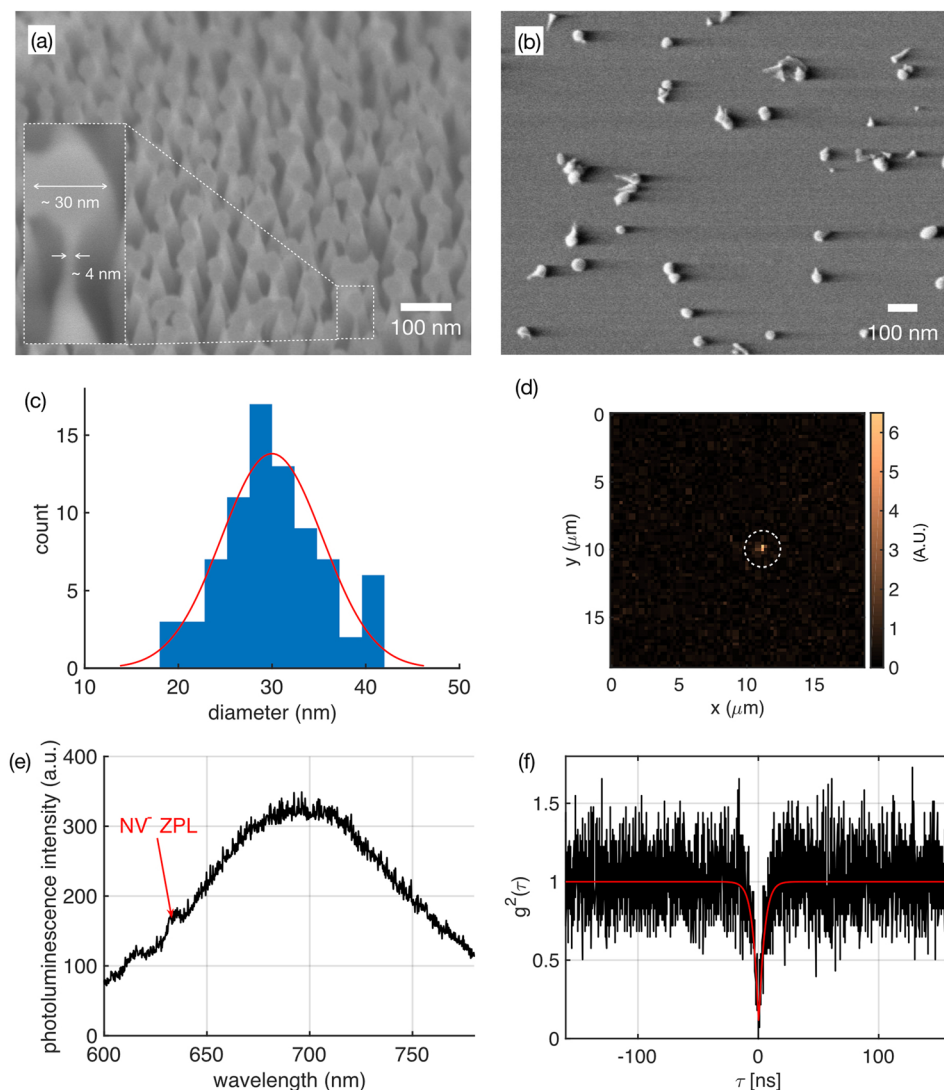


Figure 2. (a) SEM of fabricated NDs before release, featuring ~30 nm sized NDs sitting on ~4 nm diamond pedestals. (b) SEM of NDs released on glass substrate. (c) Particle size distribution histogram of NDs, determined from large scale SEM imaging and subsequent image processing to detect the size of the NDs in the SEM image. The red curve shows a Gaussian fit to the histogram with a mean diameter of 30 nm and a variance of 5.4 nm. (d) Optical confocal scanning image of the NDs released on glass substrate. The bright spot (white dashed circle) indicates an ND hosting a single NV colour centre. (e) Photoluminescence spectrum collected from the bright spot shown in (d), with the characteristic NV zero phonon line (ZPL) at 636.5 nm and a broad phonon sideband. (f) Second-order autocorrelation histogram of the collected emission from the bright spot in (d), showing $g^2(0)$ of 0.08 indicating single photon emission ($g^2(0) < 0.5$).

array of diamond pillars with a height tunable by the directional oxygen RIE duration, targeted here to 30 nm. (e) Atomic layer deposition (ALD) of SiO_2 protects the diamond pillar sidewalls. (f) Directional plasma etching of the SiO_2 using an SF_6 and O_2 gas mixture removes the SiO_2 layer at the non-sidewall surfaces. (g) Quasi-isotropic oxygen plasma etching⁴⁰ partially undercuts the bottom surface of the diamond pillars, see SI for details. At the end of this process, the ~30 nm sized diamond nanocrystals are nearly free-standing on ultrathin (~4 nm) pedestals, as shown in the close-up scanning electron micrograph (SEM) in Fig. 2a. (h) Finally, hydrofluoric (HF) acid removes the SiO_2 masks and the passivation layers, leaving the diamond nanocrystal for characterization or subsequent releasing steps.

ND size distribution. To characterize the fabricated NDs, we released the NDs on commercially available glass coverslips. We then performed large area SEM imaging of the NDs, as exemplified in Fig. 2b. Customized image processing detects single NDs on the SEM images and estimates the dimensions based on the image contrast. We evaluated over 100 NDs and visually confirmed the boundary detection results. The resultant ND diameter statistics are fitted to a Gaussian distribution curve, as shown in Fig. 2c in red. The Gaussian fit yields a mean

diameter of 30.0 nm with the 95% confidence interval from 28.8 nm to 31.2 nm, and a variance of 5.4 nm with the 95% confidence interval from 4.7 nm to 6.4 nm.

Optical characterization. The optical measurements were performed in a home-built confocal setup with 532 nm laser excitation and an excitation power of ~ 3 mW after the objective. The collection path can either be directed through a 690/40 nm notch filter to a single-photon avalanche photodiode (SPAD), or through a 561 nm long pass filter to an optical spectrometer.

Figure 2d shows a confocal scanning map of NDs released on a coverslip. The scan reveals a single bright photoluminescent spot; the corresponding spectrum collected from the bright spot, as shown in Fig. 2e, indicates a room temperature NV emission spectrum in its negative charge state with the characteristic zero phonon line (ZPL) at 636.5 nm.

Second-order autocorrelation measurements were conducted with a home built confocal setup with a 594 nm laser at ~ 200 μ W excitation power on the sample to excite the NV⁻ charge state, and a 635 nm long pass filter followed by a Nikon oil immersion objective with numerical aperture (NA) of 1.3. The second-order autocorrelation measurements ($g^{(2)}(0) \sim 0.08$) in Fig. 2f indicate emission from a single NV centre with an emission of up to 80,000 single photons per second, recorded with SPADs.

Discussion

We presented a top-down fabrication technique to produce non-aggregated monocrystalline NDs with a uniform size. The presented method enables the fabrication of NDs with a mean diameter of 30 nm and a variance of 5.4 nm. The process is performed on a IIA grade bulk diamond with a known nitrogen dopant concentration of 5 ppm. Second-order autocorrelation measurements confirm the presence of single quantum emitters in the ND.

This method can be applied to bulk diamond, diamond with tailored dopant properties, or isotopically purified diamond to produce NDs with the same dimensional properties^{41,42}. Doped NDs are attractive materials for the study of medical oncology⁴³, electrochemistry^{44,45}, diamond electronics⁴⁶, and superconductivity^{47,48}. Diamond enriched with ¹²C can enable increased coherence times of hosted spin systems due to the limited number of interfering spin impurities in the host material⁴².

The produced ND dimensions are determined by the mask patterning technique and the vertical etching step, shown in Fig. 1(d). This scalable mask patterning and etching technique is compatible for producing NDs with a wide range of dimensions and aspect ratios. The size of the dot masks obtained by BCP SA followed by SIS can be tuned from ~ 10 to ~ 30 nm in diameter by changing the SIS cycle number^{39,49}, nanoimprint lithography can be used⁵⁰ for ~ 30 –1000 nm in size, and traditional optical lithography is applicable for mask sizes beyond 1 μ m. The vertical height of the NDs can be independently controlled by the dwell time of the vertical etching in the processing step shown in Fig. 1(d).

Upon completion of the fabrication process, the NDs are non-aggregated, since the nanomask defined in the BCP SA process naturally separates one domain from another. The quasi-isotropic plasma undercut process exposes a large surface area and allows further surface treatments of the NDs. Chemical treatments such as surface modifications to minimize aggregation^{27,32} or surface functionalization for bio-binding⁵¹ are important prerequisites for a wide range of research processes and topics^{52–54}. Such surface treatments are compatible with the underlying ND fabrication method. Furthermore, different surface terminations can change the quantum properties of NV centres⁵⁵, such as a nitrogen plasma treatment⁵⁶, or can stabilize the charge state of NV centres⁵⁷, such as a fluorine-based or oxygen-based plasma treatment.

The exposed surfaces of the resulting NDs provide an opportunity to grow conformal coatings for protection or functionalization before harvesting. For example, ALD of isotopically purified SiO₂ can be used to “package” the NDs with fewer spin impurities to improve the spin coherence of the hosted NVs. Such an ALD process can be achieved with precursors such as silane⁵⁸, for which isotopically enriched sources are commercially available thanks to the well-developed silicon growth process⁵⁹. The oxidant for the SiO₂ ALD process can originate from naturally occurring oxygen. Naturally occurring oxygen has an abundance of 99.76% nuclear-spin-free ¹⁶O, higher than the naturally occurring 98.93% abundance of nuclear-spin-free ¹²C in diamond.

The estimated production yield can be scaled up using a larger area and iterating in the next depth layer of the parent diamond. This process promises large-area fabrication of NDs with size and shape uniformity, thanks to the scalability of the BCP SA process. As demonstrated in this work, the ND production yield scales with the parent diamond area size. The 70 nm pitch used in the BCP SA nanomask template translates to $\sim 2 \times 10^8$ NDs with ~ 30 nm in diameter for every 1×1 mm² diamond area. This corresponds to a production yield of ~ 9.89 ng/mm² measured in weight per unit area of the parent bulk diamond. However, the overall mass of nanodiamonds produced in this planar patterning method is of course much lower than it would be for 3D fabrication methods, such as ball-milling, though these 3D fabrication methods are unable to achieve the same size uniformity⁶⁰.

The potential impact of the presented ND fabrication technique goes beyond size uniformity and non-aggregation. The quasi-isotropic plasma undercut may induce less strain on the NDs compared to other methods for top-down fabrication of nanodiamonds^{36,37}, though further studies are required. It would also be relevant to study the spin coherence times of group IV vacancy centres hosted in NDs produced by this process¹¹. The spin coherence time T_2 of the silicon vacancy (SiV) centre is limited by the phonon-induced relaxation between two orbital ground states that are split by ~ 47 GHz⁶¹. NDs with diameters below half the corresponding phononic wavelength (~ 127 nm) may suppress the coupling of these phonon modes to prolong the SiV spin coherence times⁶². At the same time, it is important to minimize stress/strain in the NDs to maintain the defect centre's inversion symmetry such that their optical properties are preserved⁶³.

Conclusions

We realized a wide-area fabrication process in a top-down approach to produce non-aggregate monocrystalline NDs with high size uniformity. Additional optical characterization confirmed the existence of single NVs hosted in the NDs by probing their photoluminescence spectra and photon statistics. The fabrication technique applies to a broad range of engineered bulk diamond, including for example isotopically purified substrates. ¹²C enriched diamond hosted spin systems have been shown to greatly extend the NV electron spin coherence time^{36,37}.

Data Availability

The data that support the findings of this study are available upon reasonable request.

References

- Pingault, B. *et al.* Coherent control of the silicon-vacancy spin in diamond. *Nat. Commun.* **8**, 15579 (2017).
- Iwasaki, T. *et al.* Germanium-Vacancy Single Color Centers in Diamond. *Sci. Rep.* **5**, 12882 (2015).
- Widmann, M. *et al.* Coherent control of single spins in silicon carbide at room temperature. *Nat. Mater.* **14**, 164–168 (2015).
- Lienhard, B. *et al.* Bright and photostable single-photon emitter in silicon carbide. *Optica*, *OPTICA* **3**, 768–774 (2016).
- Schröder, T. *et al.* Quantum nanophotonics in diamond [Invited]. *J. Opt. Soc. Am. B*, *JOSAB* **33**, B65–B83 (2016).
- Atatüre, M., Englund, D., Vamivakas, N., Lee, S.-Y. & Wrachtrup, J. Material platforms for spin-based photonic quantum technologies. *Nature Reviews Materials* **3**, 38–51 (2018).
- Humphreys, P. C. *et al.* Deterministic delivery of remote entanglement on a quantum network. *Nature* **558**, 268–273 (2018).
- Degen, C. L., Reinhard, F. & Cappellaro, P. Quantum sensing. *Rev. Mod. Phys.* **89**, 035002 (2017).
- Sipahigil, A. *et al.* An integrated diamond nanophotonics platform for quantum-optical networks. *Science* **354**, 847–850 (2016).
- Bhaskar, M. K. *et al.* Quantum nonlinear optics with a germanium-vacancy color center in a nanoscale diamond waveguide. *Phys. Rev. Lett.* **118**, 223603 (2017).
- Iwasaki, T. *et al.* Tin-Vacancy Quantum Emitters in Diamond. *Phys. Rev. Lett.* **119**, 253601 (2017).
- Trusheim, M. E. *et al.* Lead-Related Quantum Emitters in Diamond. *Phys. Rev. B* **99**, 075430 (2019).
- Haziza, S. *et al.* Fluorescent nanodiamond tracking reveals intraneuronal transport abnormalities induced by brain-disease-related genetic risk factors. *Nat. Nanotechnol.* **12**, 322–328 (2017).
- Mochalin, V. N., Shenderova, O., Ho, D. & Gogotsi, Y. The properties and applications of nanodiamonds. *Nat. Nanotechnol.* **7**, 11–23 (2011).
- Rogers, L. J. *et al.* Single SiV⁻ centers in low-strain nanodiamonds with bulk-like spectral properties and nano-manipulation capabilities. *arXiv [cond-mat.mes-hall]* (2018).
- Knowles, H. S., Kara, D. M. & Atatüre, M. Observing bulk diamond spin coherence in high-purity nanodiamonds. *Nat. Mater.* **13**, 21–25 (2013).
- Krueger, A. & Lang, D. Functionality is key: recent progress in the surface modification of nanodiamond. *Adv. Funct. Mater.* **22**, 890–906 (2012).
- Johnson, S. *et al.* Tunable cavity coupling of the zero phonon line of a nitrogen-vacancy defect in diamond. *New J. Phys.* **17**, 122003 (2015).
- Neukirch, L. P., von Haartman, E., Rosenholm, J. M. & Nick Vamivakas, A. Multi-dimensional single-spin nano-optomechanics with a levitated nanodiamond. *Nat. Photonics* **9**, 653 (2015).
- Yin, Z.-Q., Li, T., Zhang, X. & Duan, L. M. Large quantum superpositions of a levitated nanodiamond through spin-optomechanical coupling. *Phys. Rev. A* **88**, 033614 (2013).
- Pelliccione, M., Myers, B. A., Pascal, L. M. A., Das, A. & Bleszynski Jayich, A. C. Two-Dimensional Nanoscale Imaging of Gadolinium Spins via Scanning Probe Relaxometry with a Single Spin in Diamond. *Phys. Rev. Applied* **2**, 054014 (2014).
- Tetienne, J.-P. *et al.* Scanning Nanospin Ensemble Microscope for Nanoscale Magnetic and Thermal Imaging. *Nano Lett.* **16**, 326–333 (2016).
- Laraoui, A. *et al.* Imaging thermal conductivity with nanoscale resolution using a scanning spin probe. *Nat. Commun.* **6**, 8954 (2015).
- Rabeau, J. R. *et al.* Single nitrogen vacancy centers in chemical vapor deposited diamond nanocrystals. *Nano Lett.* **7**, 3433–3437 (2007).
- Liu, W. *et al.* Fluorescent Nanodiamond–Gold Hybrid Particles for Multimodal Optical and Electron Microscopy Cellular Imaging. *Nano Lett.* **16**, 6236–6244 (2016).
- Huang, H., Dai, L., Wang, D. H., Tan, L.-S. & Osawa, E. Large-scale self-assembly of dispersed nanodiamonds. *J. Mater. Chem.* **18**, 1347–1352 (2008).
- Zhang, T. *et al.* DNA-Based Self-Assembly of Fluorescent Nanodiamonds. *J. Am. Chem. Soc.* **137**, 9776–9779 (2015).
- Shiryaev, A. A. *et al.* Ion implantation in nanodiamonds: size effect and energy dependence. *Sci. Rep.* **8**, 5099 (2018).
- Turcheniuk, K., Trecuzzi, C., Deeleejjananan, C. & Mochalin, V. N. Salt-Assisted Ultrasonic Deaggregation of Nanodiamond. *ACS Appl. Mater. Interfaces* **8**, 25461–25468 (2016).
- Wolters, J. *et al.* Enhancement of the zero phonon line emission from a single nitrogen vacancy center in a nanodiamond via coupling to a photonic crystal cavity. *Appl. Phys. Lett.* **97**, 141108 (2010).
- Kucsko, G. *et al.* Nanometre-scale thermometry in a living cell. *Nature* **500**, 54–58 (2013).
- Edgington, R. *et al.* Functionalisation of Detonation Nanodiamond for Monodispersed, Soluble DNA-Nanodiamond Conjugates Using Mixed Silane Bead-Assisted Sonication Disintegration. *Sci. Rep.* **8**, 728 (2018).
- Bevilacqua, M. *et al.* Nanocrystalline diamond as an electronic material: An impedance spectroscopic and Hall effect measurement study. *J. Appl. Phys.* **107**, 033716 (2010).
- Frangeskou, A. C. *et al.* Optical levitation of high purity nanodiamonds in vacuum without heating. *arXiv [physics.optics]* (2016).
- Shenderova, O. A. *et al.* Nitrogen Control in Nanodiamond Produced by Detonation Shock-Wave-Assisted Synthesis. *J. Phys. Chem. C* **115**, 14014–14024 (2011).
- Trusheim, M. E. *et al.* Scalable fabrication of high purity diamond nanocrystals with long-spin-coherence nitrogen vacancy centers. *Nano Lett.* **14**, 32–36 (2014).
- Andrich, P. *et al.* Engineered micro- and nanoscale diamonds as mobile probes for high-resolution sensing in fluid. *Nano Lett.* **14**, 4959–4964 (2014).
- Kamcev, J. *et al.* Chemically enhancing block copolymers for block-selective synthesis of self-assembled metal oxide nanostructures. *ACS Nano* **7**, 339–346 (2013).
- Peng, Q., Tseng, Y.-C., Darling, S. B. & Elam, J. W. Nanoscopic patterned materials with tunable dimensions via atomic layer deposition on block copolymers. *Adv. Mater.* **22**, 5129–5133 (2010).
- Khanaliloo, B. *et al.* Single-Crystal Diamond Nanobeam Waveguide Optomechanics. *Phys. Rev. X* **5**, 041051 (2015).
- Balasubramanian, G. *et al.* Ultralong spin coherence time in isotopically engineered diamond. *Nat. Mater.* **8**, 383–387 (2009).
- Ishikawa, T. *et al.* Optical and spin coherence properties of nitrogen-vacancy centers placed in a 100 nm thick isotopically purified diamond layer. *Nano Lett.* **12**, 2083–2087 (2012).

43. Vervald, A. M. *et al.* Boron-doped nanodiamonds as possible agents for local hyperthermia. *Laser Phys. Lett.* **14**, 045702 (2017).
44. Holt, K. B., Caruana, D. J. & Millán-Barrios, E. J. Electrochemistry of undoped diamond nanoparticles: accessing surface redox states. *J. Am. Chem. Soc.* **131**, 11272–11273 (2009).
45. Pichot, V. *et al.* High Nitrogen Doping of Detonation Nanodiamonds. *J. Phys. Chem. C* **114**, 10082–10087 (2010).
46. Terranova, M. L., Orlanducci, S., Rossi, M. & Tamburri, E. Nanodiamonds for field emission: state of the art. *Nanoscale* **7**, 5094–5114 (2015).
47. Zhang, G. *et al.* Superconducting Ferromagnetic Nanodiamond. *ACS Nano* **11**, 5358–5366 (2017).
48. Ekimov, E. A. *et al.* Superconductivity in diamond. *Nature* **428**, 542–545 (2004).
49. Yin, J., Xu, Q., Wang, Z., Yao, X. & Wang, Y. Highly ordered TiO₂ nanostructures by sequential vapour infiltration of block copolymer micellar films in an atomic layer deposition reactor. *J. Mater. Chem.* **1**, 1029–1036 (2013).
50. Chou, S. Y., Krauss, P. R. & Renstrom, P. J. Imprint Lithography with 25-Nanometer Resolution. *Science* **272**, 85–87 (1996).
51. Vajjayanthimala, V., Tzeng, Y.-K., Chang, H.-C. & Li, C.-L. The biocompatibility of fluorescent nanodiamonds and their mechanism of cellular uptake. *Nanotechnology* **20**, 425103 (2009).
52. Hemelaar, S. R. *et al.* Nanodiamonds as multi-purpose labels for microscopy. *Sci. Rep.* **7**, 720 (2017).
53. Karaveli, S. *et al.* Modulation of nitrogen vacancy charge state and fluorescence in nanodiamonds using electrochemical potential. *Proc. Natl. Acad. Sci. USA*, <https://doi.org/10.1073/pnas.1504451113> (2016).
54. Chen, E. H., Gaathon, O., Trusheim, M. E. & Englund, D. Wide-field multispectral super-resolution imaging using spin-dependent fluorescence in nanodiamonds. *Nano Lett.* **13**, 2073–2077 (2013).
55. Ryan, R. G. *et al.* Impact of Surface Functionalization on the Quantum Coherence of Nitrogen-Vacancy Centers in Nanodiamonds. *ACS Appl. Mater. Interfaces* **10**, 13143–13149 (2018).
56. Chou, J.-P., Retzker, A. & Gali, A. Nitrogen-Terminated Diamond (111) Surface for Room-Temperature Quantum Sensing and Simulation. *Nano Lett.* **17**, 2294–2298 (2017).
57. Cui, S. & Hu, E. L. Increased negatively charged nitrogen-vacancy centers in fluorinated diamond. *Appl. Phys. Lett.* **103**, 051603 (2013).
58. Burton, B. B., Kang, S. W., Rhee, S. W. & George, S. M. SiO₂ Atomic Layer Deposition Using Tris(dimethylamino)silane and Hydrogen Peroxide Studied by *in Situ* Transmission FTIR Spectroscopy. *J. Phys. Chem. C* **113**, 8249–8257 (2009).
59. Li, J.-Y., Huang, C.-T., Rokhinson, L. P. & Sturm, J. C. Extremely high electron mobility in isotopically-enriched ²⁸Si two-dimensional electron gases grown by chemical vapor deposition. *Appl. Phys. Lett.* **103**, 162105 (2013).
60. Mahfouz, R. *et al.* Size-controlled fluorescent nanodiamonds: a facile method of fabrication and color-center counting. *Nanoscale* **5**, 11776–11782 (2013).
61. Rogers, L. J. *et al.* All-optical initialization, readout, and coherent preparation of single silicon-vacancy spins in diamond. *Phys. Rev. Lett.* **113**, 263602 (2014).
62. Jahnke, K. D. *et al.* Electron–phonon processes of the silicon-vacancy centre in diamond. *New J. Phys.* **17**, 043011 (2015).
63. Rogers, L. J. *et al.* Single Si-V Centers in Low-Strain Nanodiamonds with Bulklike Spectral Properties and Nanomanipulation Capabilities. *Physical Review Applied* **11**, 024073 (2019).

Acknowledgements

The conducted research was supported in part by the Army Research office MURI biological transduction program and NSF Center for Integrated Quantum Materials. Research carried out in part at the Center for Functional Nanomaterials, Brookhaven National Laboratory, which is supported by the U.S. Department of Energy, Office of Basic Energy Sciences, under Contract No. DE-SC0012704. J.Z. was supported in part by Master Dynamic, Inc.

Author Contributions

J.Z. and G.D. developed the fabrication technique. H.S.K., Y.-C.B. and J.K. conducted the atomic layer deposition of silicon dioxide. B.L., J.Z. and M.C. characterized the fabricated sample. C.-Y.N. and G.D. trained J.Z. on the cleanroom and nanofabrication facilities. J.Z. and B.L. wrote the manuscript in consultation with E.B. and D.E. C.T.B. and D.E. supervised the project. All the authors commented and revised the manuscript.

Additional Information

Supplementary information accompanies this paper at <https://doi.org/10.1038/s41598-019-43304-5>.

Competing Interests: The authors declare no competing interests.

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2019